

## ASTM D695 Compressive Properties of Plastics

### TEST METHOD SUMMARY

ASTM D695 examines the compressive properties of reinforced and unreinforced rigid plastics, including high-modulus composites, through a process of straining and loading the plastic at relatively low rates of strain. It enables replication of application-specific conditions. The compressive property information provides a standard and consistent means to compare materials for research and development, quality control, acceptance or rejection under specifications, and other material evaluation processes.

Critical compressive properties include modulus of elasticity, yield stress, deformation beyond yield point, and compressive strength (unless the material merely flattens but does not fracture). According to ASTM D695, the specimen is placed between compressive plates parallel to the specimen surface, and compressed along its major axis at constant rate of displacement until the specimen fractures or until the load or the decrease in length reaches a predetermined value. An extensometer attached to the fixture is used to determine the modulus of elasticity. When performing compression testing, it has been found that specimen alignment plays an important role in achieving even load distribution, which contributes to the consistency of the results.

Solutions for ASTM D695 typically include these types of components;

### LOAD FRAME OPTIONS\*

Both the premium MTS Criterion® and the economical MTS Exceed® universal testing machines are ideal for determining the compressive properties of plastics per ASTM D695. They both come in a variety of force capacities and frame styles, ranging from 1-column tabletops to larger 2-column floor-standing models. The 30kN and 100kN models also have dual-zone test spaces to reduce set-up times if you frequently change test requirements. And as an alternative to a new load frame, you can modernize the software and controls of your old test system with an MTS ReNew™ Upgrade.



MTS Criterion®  
Electromechanical Universal Test Systems



MTS Exceed®  
Electromechanical Universal Test Systems

### COMPRESSION PLATEN OPTIONS\*

Room Temperature Testing	Temperature Testing
Compression platens are generally selected based on the required compression of the test specimen. As examples, these compression platens are designed for up to 20kN of force	Compression platens for temperature testing between -70°C to 350°C (-94°F to 662°F) are available as a one fixed / one spherically seated platen combination.

### Thin Sample Guided Compression Fixture\*


When compression testing thin samples a guided compression fixture is often used to hold the sample between the platens. The MTS 605.30 Guided Compression Fixture has accommodation for use of a MTS 632.17 Axial Averaging Extensometer.

### EXTENSOMETRY OPTIONS\*

Platen-to-platen Displacement	Non-contact Video Strain	Simple platen-to-platen measurement is often sufficient for most tests.
		MTS can also offer advanced non-contact strain measurement using the Advantage Video Extensometer.

## CHAMBER OPTIONS\*

	
<b>Advantage Environmental Chamber</b>	<b>FEC 1200 or 1300</b>
The Advantage™ Environmental Chamber designed for Criterion load frames is ideal for testing of elastomeric components, tire cords, plastics, composites, and laminates. It has a temperature range from -129° C to 315° C (-200°F to 600°F), and is compatible with either video or laser extensometers.	The Fundamental™ Environmental Chamber designed for Exceed load frames is also ideal for testing these same thermoplastic and composite materials. It has a temperature range from -70°C to 350°C (-94°F to 662°F) and is likewise compatible with either video or laser extensometers.

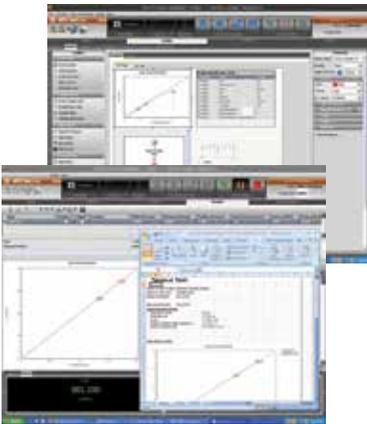

## SOFTWARE OPTIONS\*

<b>ASTM D695 Compressive Properties Test Template</b>	<b>About TestSuite™ TW</b>
To simplify testing to ASTM D695, MTS has developed a TestSuite™ TW test template that will set-up and run the recommended compression tests. After the test data has been collected, reports can display all of the required calculations including compressive strength, compressive yield strength, offset yield strength, modulus of elasticity, and more.  MTS consultants are also available to support any of your plastic and composite compression test applications, test method set-up, and data collection and integration requirements.	This flexible and versatile software package comes in three versions so that you can choose exactly which one best fits your requirements. Lab managers and test creators like TW Elite since it includes all the test definition capacity and flexibility needed to create and edit custom test sequences while accommodating the specific runtime needs of lab personnel. Test operators prefer the simplicity and intuitive nature of TW Express. This software allows operators to easily execute tests and monitor data or calculate values in runtime views. For QA/QC labs that prefer the Exceed universal test machine, TW Essential will provide both the test creation and test operation capabilities, combining efficiency and productivity in one software application.

\*NOTE: This technical note is intended to show some of the popular and more common solutions used for this particular application. Most of the time, additional options are available and necessary to accomplish your more comprehensive test objectives.

## APPENDIX - TEST SPECIMEN DETAIL

Most Common Specimen Sizes	Distance between Platens (mm)	Width & Length (mm)
Measuring Strength	25.4	12.7
Measuring Modulus	50.8	12.7



**MTS Systems**  
 14000 Technology Drive  
 Eden Prairie, MN 55344-2290 USA  
 Telephone: 1-952-937-4000  
 Toll Free: 1-800-328-2255  
 E-mail: info@mts.com  
 www.mts.com

ISO 9001 Certified QMS

MTS, MTS Criterion, and MTS Exceed are registered trademarks, and TestSuite and ReNew are trademarks of MTS Systems within the United States. These trademarks may be protected in other countries. RTM No. 211177.

©2021 MTS Systems  
 100-332-868 TMTND695 Printed in U.S.A. 09/21